

PAPER • OPEN ACCESS

Qualitative investigations on the stability of Al_2O_3 - SiO_2 hybrid water-based nanofluids

To cite this article: H Ismail *et al* 2020 *IOP Conf. Ser.: Mater. Sci. Eng.* **788** 012091

View the [article online](#) for updates and enhancements.

INTERNATIONAL OPEN ACCESS WEEK
OCTOBER 19-26, 2020

ALL ECS ARTICLES. ALL FREE. ALL WEEK.
www.ecsdl.org

**NOW
AVAILABLE**

Qualitative investigations on the stability of Al₂O₃-SiO₂ hybrid water-based nanofluids

H Ismail¹, M Z Sulaiman^{1,*} and M A H Aizzat¹

¹ Faculty of Mechanical and Automotive Engineering Technology, Universiti Malaysia Pahang, 26600 Pekan, Pahang, Malaysia

*Corresponding author: zuhairi@ump.edu.my

Abstract. Qualitative experiments were carried out to investigate the stability of Al₂O₃-SiO₂ hybrid water-based nanofluids. The main nanoparticles used in this work were Al₂O₃ and SiO₂ since these types of nanoparticles has been widely used and proposed in many applications and information on their hybrid dispersion stability characteristic are still elusive. The present work demonstrated the stability of Al₂O₃-SiO₂ hybrid nanofluids using various preparation techniques and successively elucidating the optimum preparation method for hybrid nanofluid. The hybrid water-based nanofluid were prepared by dispersing a 50:50 ratio of Al₂O₃-SiO₂ nanoparticles into distilled water to achieve total volume concentration of C=0.001, 0.01 and 0.1 vol%. Successively, the hybrid nanofluids were prepared using magnetic stirrer and ultrasonic bath. The samples are categorised into five preparation method which are: (i) 1 hour sonication, (ii) 1 hour magnetic stirrer, (iii) 0.25 hour magnetic stirrer and 1 hour sonication, and (iv) 0.5 hour magnetic stirrer and 1 hour sonication and (v) without magnetic stirring and sonication. The height of sedimentation and colloidal stability of each preparation methods were observed in the duration of 2 weeks. In the present work, it was observed that the dispersion stability of hybrid nanofluids prepared by applying magnetic stirrer for 15 minutes with prior to 1 hour of sonication had demonstrated the highest stability indicated by the lowest height of sedimentation and high colloidal stability.

Keywords. Aluminium oxide; Silicon dioxide; Metal oxide hybrid nanofluids; Stability

1. Introduction

Nanoparticles can be defined as particles with less than 100nm size in at least 1 dimension. When nanoparticles are formed, the properties of many conventional materials change. This is usually because nanoparticles have a larger surface area per weight than larger particles, making them more reactive to other molecules. The study on nanoparticles are flourishing in the recent years with its numerous application in industries such as biomedical, optical and engineering fields, prompting researchers to develop ways to include nanoparticles for industrial application. However, it is quite difficult to obtain a stable dispersion of nanoparticles in the base fluid, which makes it important to understand the interaction that occurs between particle-particle and particle-liquid in order to prepare a stable fluid. Due to the attractive and repulsive forces on the particle surface, it generates different kinds of interactions among the particles involved. The most dominant forces would be the attractive molecular



forces, which causes particles to clump together, which is termed as agglomeration. Hence, these agglomerates reduce the stability of the nanofluids prepared.

Particles that were dispersed in a base fluid have a tendency to form larger aggregates and adhere together which may produce settlement due to gravitational forces which is also named as colloidal dispersion. A colloid can be liquid-liquid mixture or solid-liquid mixture. These would affect the stability of the prepared nanofluids. In order to determine the stability of nanofluids, one of the widely used methods by different researchers in literature is the sedimentation analysis or sediment ratio of nanoparticles [1–4]. This can be obtained by observing the rate of aggregation of the nanoparticles suspended in the base fluid. Sedimentation analysis is one of the methods in which many researchers opt for in order to obtain the stability of the nanofluids that they prepared. It was proven to be one of the reliable methods in determining a stability of a dispersion [5].

In general, the rate of aggregation is determined by the probability of cohesion and the frequency of collisions in fluids. A theory for colloidal stability was developed by Derjaguin, Landau, Verwey and Overbeek (DLVO) [6–8]. The theory suggests that the stability of a particle in solution is determined by the sum of van der Waals attractive and electrical double layer repulsive forces that exist between particles as they approach each other due to the Brownian motion they are undergoing. To reduce these forces, the morphological characteristics of nanofluids are highly affected by the intensity of stirring and sonication time during its preparation.

Most of the researchers tend to add surfactant during preparation of nanofluids, which acts as dispersant, and reducing the agglomeration of nanoparticles in base fluid. In addition, the preparation method and choice of nanoparticles used also could highly affect the stability of nanofluids. Recently, many researchers utilized ultrasonic and stirring techniques for preparing nanofluids in either one-step or two-step methods [9–15]. Ultrasonic technique is commonly used to agitate and disperse nanoparticles into finer particles in the base fluid. S. Suresh et al. [16] studied the stability of spherical Al_2O_3 nanoparticles in deionized water after 6 hours of sonication at a concentration of 0.1 vol%. The author stated that the prepared nanofluids were stable for several weeks without any visible sedimentation. Xia et al. [17] reported that when using two different types of surfactant under the same ultrasonic intensity during preparation of Al_2O_3 nanofluids, the suspension with non-ionic surfactant shows better dispersion and longer stability as compared with anionic surfactant after 48 hours. Verma and Tiwari [18] in their studies revealed that by using ultrasonic method only, the prepared SiO_2 nanofluids contain some agglomeration and lumping of nanoparticles. Despite that, the agglomerated lumps were in the nanosize range. In addition, Leena and Srinivasan [19] reported that the ultrasonic velocity increases with an increase in concentrations of TiO_2 nanofluids. Hence, it shows that with an increasing concentration of nanoparticles used, a much greater agitation is needed to overcome the agglomeration of particles in the base fluids.

Other than focusing on single type of nanoparticles, numerous studies on hybrid nanofluids is becoming more common, with a vast mixture of different types of nanoparticles [20–22]. Maddah et al. [23] analyzed the stability of hybrid Al_2O_3 - TiO_2 nanoparticles in distilled water after 5 hours of sonication. The author found that the nanoparticles were homogeneously mixed in the base fluid and it had sufficient stability. Moldoveanu et al. [24] studied on the thermal performance of stabilized Al_2O_3 - SiO_2 nanofluids prepared using one-step method and 1 hour of sonication. They reported that the prepared nanofluids were found to be relatively stable for about ten days. Although there are many reports available on the preparation method of nanofluids, none of them focused on finding the most suitable method to prepare stable hybrid nanofluids. In the present work, an attempt has been made to study the stability of hybrid Al_2O_3 - SiO_2 nanofluids in distilled water prepared using two-step method with different mechanical stabilizing techniques.

2. Methodology

2.1 Preparation of nanofluids

The nanopowder used in this experiment were (1) Aeroxide Alu C (Aluminium Oxide, Al_2O_3) particles with d_p of 13nm and (2) Aerosil 90 (Silicon Dioxide, SiO_2) particles with d_p of 20nm, obtained from

Aerosil Corporation. In the present experiment, the stated nanoparticles were mixed to achieve a hybrid $\text{Al}_2\text{O}_3\text{-SiO}_2\text{/water}$ nanofluids of 50:50 vol% ratio which results in a concentration of 0.001, 0.01 and 0.1 vol%. The three concentration variations, $C = 0.001, 0.01$ and 0.1 vol% were defined as low (L), medium (M) and high (H) concentration respectively.

Using two-step method, the nanoparticle powder were dispersed into 150ml distilled water inside a beaker. Then, 25ml of the nanofluids were transferred into 5 different test tubes. Successively, each test tube contains nanofluids with different preparation methods and labelled as (i), (ii), (iii), (iv) and (v) where test tube (i) represents the nanofluids that was sonicated for 1 hour, test tube (ii) is the nanofluids prepared using 1 hour of magnetic stirring while the nanofluids in test tube (v) did not undergo any stabilizing techniques. As for test tubes labelled (iii) and (iv), the nanofluids were prepared by implementing both magnetic stirring and sonication method. The nanofluids in test tubes (iii) and (iv) undergoes 0.25 and 0.5 hour of magnetic stirring using magnetic stirrer (FAVORIT Stirring Hotplate) respectively. The nanofluids were then sonicated for 1 hour using an ultrasonic agitator (Bransonic® CPXH Ultrasonic Bath). All of the nanofluids prepared were milky in colour with a darker gradient for higher concentrations. Table 1 presents the preparation method that the author used for this study.

Table 1. Preparation method for hybrid $\text{Al}_2\text{O}_3\text{-SiO}_2\text{/water}$ nanofluids of 50:50 ratio at different concentrations.

Nanoparticle	Concentration (vol%)	Method	Types
$\text{Al}_2\text{O}_3\text{-SiO}_2$	0.001	1 hour ultrasonic	L(i)
		1 hour magnetic stirrer	L(ii)
		0.25 hour magnetic stirrer + 1 hour ultrasonic	L(iii)
		0.5 hour magnetic stirrer + 1 hour ultrasonic	L(iv)
		None	L(v)
$\text{Al}_2\text{O}_3\text{-SiO}_2$	0.01	1 hour ultrasonic	M(i)
		1 hour magnetic stirrer	M(ii)
		0.25 hour magnetic stirrer + 1 hour ultrasonic	M(iii)
		0.5 hour magnetic stirrer + 1 hour ultrasonic	M(iv)
		None	M(v)
$\text{Al}_2\text{O}_3\text{-SiO}_2$	0.1	1 hour ultrasonic	H(i)
		1 hour magnetic stirrer	H(ii)
		0.25 hour magnetic stirrer + 1 hour ultrasonic	H(iii)
		0.5 hour magnetic stirrer + 1 hour ultrasonic	H(iv)
		None	H(v)

2.2 Sedimentation measurement

In this experiment, sonication time were set to 1 hour, while the stirring time were set to 0.25 and 0.5 hour. The $\text{Al}_2\text{O}_3\text{-SiO}_2\text{/water}$ hybrid nanofluids were observed for 0, 12, 24 hour and 2 weeks after its preparation. The height of the sedimentation of the nanoparticles were observed by using photographic capturing of the prepared nanofluids in a glass test tube of 30ml volume. There were no manipulation of the test tubes during the observation process and the evaporation of the prepared nanofluids were prevented by using a screw-type cap test tubes (KIMAX).

3. Results and discussion

Based on figure 1, the test tubes were arranged starting from the left with test tubes labelled (i)-(v) consecutively. The configurations were the same for each concentrations. Figure 1(a) shows the sedimentation observations for the $\text{Al}_2\text{O}_3\text{-SiO}_2$ /water hybrid nanofluids at 0.001 vol%. After 2 weeks of observations, only slight agglomeration could be noticed in all of the test tube. Due to the small amount of nanoparticles used for this concentration, there is nearly no concluded observation could be drawn since the transparency of the nanofluids is similar to the distilled water used.

At concentration of 0.01 vol%, it can be seen that the stability of the nanofluids in test tube M(i) deteriorates after 6 hours with less nanoparticles suspended in the fluid, and hence producing a clear layer as shown in figure 1(b). From the observation, it can be seen that the sample in test tube labelled M(iii) and M(iv) had the highest stability with less settlement of nanoparticles at the bottom of the test tube. After 12 hour of preparation, clear layer started to form on all methods of preparation, but with the least formation of clear layer can be seen in test tube labelled M(iii) while the most visible layer could be seen in test tube M(i) as shown in figure 1(b). At 2 weeks of preparation, test tube labelled M(iii) had the highest colloidal stability, with lowest amount of sedimentation and clear layer formed. For concentration 0.01 vol%, it can be concluded that by implementing sonication and stirring method, it significantly improves the stability of the nanofluids prepared.

Figure 1(c) shows the sedimentation analysis for 0.1 vol% of the prepared hybrid nanofluids. After 12 hour of preparation, all of the nanofluids showed signs of slight phase separation, with the formation of clear layer in the test tube. Even though test tube H(ii) showed little to no signs of clear layer, it has the most amount of sedimentation, and becomes unstable. At 24 hours after preparation, it can be seen that the phase separation occurs more vigorously during this period. The clear layer of fluids appear to be more visible in each method of preparations, with test tube H(i) has the most obvious clear layer, followed by H(v), H(iv), H(iii) and H(ii). After 2 weeks, pictures are taken and it is found that settling velocity of nanoparticles prepared using both stirring and sonication is much lower than the others, as seen in test tube labelled H(iii) and H(iv). Clear layer is still visible for the samples, but the ratio of sedimentation is much lower than that of sample prepared without using both methods. In conclusion, the highest stability of dispersion of nanoparticles can be achieved by using the stirring and sonication method.

4. Conclusions

In this study, the stability of $\text{Al}_2\text{O}_3\text{-SiO}_2$ hybrid nanofluid of 50:50 ratio were observed by using sedimentation analysis. The nanofluid were prepared using two-step method to achieve a concentration of 0.001, 0.01 and 0.1 vol%.

- It can be concluded that the dispersion stability of hybrid nanofluids prepared by applying magnetic stirrer prior to sonication had demonstrated the lowest height of sedimentation despite of the concentration of hybrid nanoparticles used. Even after repetitive experimentation, the results obtained for sedimentation remains the same.
- Method (iii) which is using 15 minutes magnetic stirring and 1 hour of sonication is considered sufficient in producing a stable nanofluids. This can be proven by the smaller aggregates of particles, which reduces the settling rate of the nanoparticles to gravity and hence produces the optimal aggregation of nanoparticles.

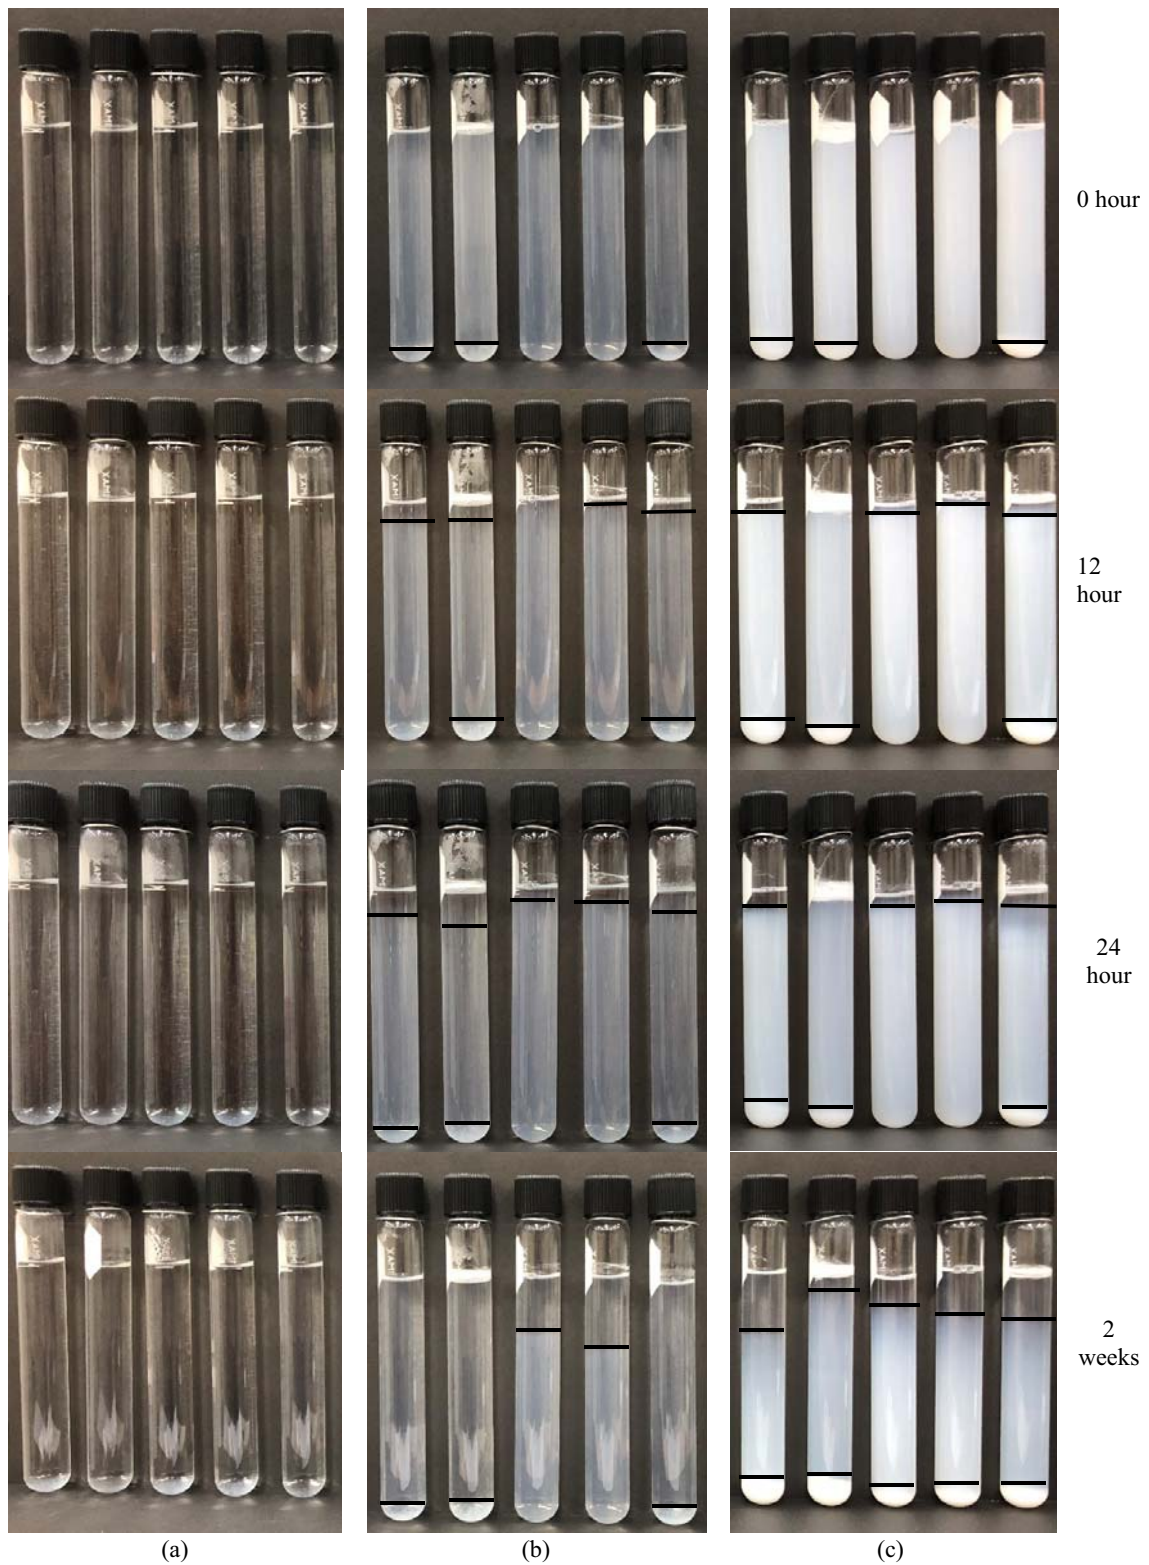


Figure 1. The prepared hybrid $\text{Al}_2\text{O}_3\text{-SiO}_2$ nanofluids of 50:50 ratio at (a) 0.001 vol%, (b) 0.01 vol% and (c) 0.1 vol% using different preparation method.

Acknowledgement

Financial support by Universiti Malaysia Pahang (www.ump.edu.my) under RDU160385, PGRS1903157 and Malaysian Ministry of Education under FRGS (FRGS/1/2017/TK07/UMP/03/1)/ (RDU170136) are gratefully acknowledged.

References

- [1] Ozsoy A and Corumlu V 2018 Thermal performance of a thermosyphon heat pipe evacuated tube solar collector using silver-water nano fluid for commercial applications *Renew. Energy* **122** 26–34
- [2] Karthikeyan A, Coulombe S and Kietzig A M 2018 Boiling heat transfer enhancement with stable nanofluids and laser textured copper surfaces *Int. J. Heat Mass Transf.* **126** 287–96
- [3] Yan S, Wang F, Shi Z G and Tian R 2017 Heat transfer property of SiO₂/water nanofluid flow inside solar collector vacuum tubes *Appl. Therm. Eng.* **118** 385–91
- [4] Oliveira L R, Silva A C A, Dantas N O and Bandarra Filho E P 2017 Thermophysical properties of TiO₂-PVA/water nanofluids *Int. J. Heat Mass Transf.* **115** 795–808
- [5] Kumar R S and Sharma T 2018 Stability and rheological properties of nanofluids stabilized by SiO₂ nanoparticles and SiO₂-TiO₂ nanocomposites for oilfield applications *Colloids Surfaces A Physicochem. Eng. Asp.* **539** 171–83
- [6] Missana T and Adell A 2000 On the applicability of DLVO theory to the prediction of clay colloids stability *J. Colloid Interface Sci.* **230** 150–6
- [7] Popa I, Gillies G, Papastavrou G and Borkovec M 2010 Attractive and repulsive electrostatic forces between positively charged latex particles in the presence of anionic linear polyelectrolytes *J. Phys. Chem. B* **114** 3170–7
- [8] Khairul M A, Shah K, Doroodchi E, Azizian R and Moghtaderi B 2016 Effects of surfactant on stability and thermo-physical properties of metal oxide nanofluids *Int. J. Heat Mass Transf.* **98** 778–87
- [9] Mo S, Chen Y, Jia L and Luo X 2012 Investigation on crystallization of TiO₂-water nanofluids and deionized water *Appl. Energy* **93** 65–70
- [10] Kumaresan V and Velraj R 2012 Experimental investigation of the thermo-physical properties of water-ethylene glycol mixture based CNT nanofluids *Thermochim. Acta* **545** 180–6
- [11] Hajjar Z, Rashidi A morad and Ghoozati A 2014 Enhanced thermal conductivities of graphene oxide nanofluids *Int. Commun. Heat Mass Transf.* **57** 128–31
- [12] Gopal V R V and Kamila S 2016 ScienceDirect Synthesis and characterization of nano particles and nanofluids : A comparative study *Mater. Today Proc.* **3** 2457–62
- [13] Das P K, Islam N, Santra A K and Ganguly R 2017 Experimental investigation of thermophysical properties of Al₂O₃-water nanofluid: Role of surfactants *J. Mol. Liq.* **237** 304–12
- [14] Esfahani N N, Toghraie D and Afrand M 2018 A new correlation for predicting the thermal conductivity of ZnO–Ag (50%–50%)/water hybrid nanofluid: An experimental study *Powder Technol.* **323** 367–73
- [15] Gangadevi R, Vinayagam B K and Senthilraja S 2018 Effects of sonication time and temperature on thermal conductivity of CuO/water and Al₂O₃/water nanofluids with and without surfactant *Mater. Today Proc.* **5** 9004–11
- [16] Chandrasekar M, Suresh S and Bose A C 2011 Experimental studies on heat transfer and friction factor characteristics of Al₂O₃/water nanofluid in a circular pipe under transition flow with wire coil inserts *Heat Transf. Eng.* **32** 485–96
- [17] Xia G, Jiang H, Liu R and Zhai Y 2014 Effects of surfactant on the stability and thermal conductivity of Al₂O₃/de-ionized water nanofluids *Int. J. Therm. Sci.* **84** 118–24
- [18] Verma S K and Tiwari A K 2017 Characterization of Nanofluids as an advanced heat transporting medium for Energy Systems *Mater. Today Proc.* **4** 4095–103
- [19] Leena M and Srinivasan S 2015 Synthesis and ultrasonic investigations of titanium oxide nanofluids *J. Mol. Liq.* **206** 103–9

- [20] Moldoveanu G M, Ibanescu C, Danu M and Minea A A 2018 Viscosity estimation of Al₂O₃, SiO₂nanofluids and their hybrid: An experimental study *J. Mol. Liq.* **253** 188–96
- [21] Moldoveanu G M, Minea A A, Iacob M, Ibanescu C and Danu M 2018 Experimental study on viscosity of stabilized Al₂O₃, TiO₂ nanofluids and their hybrid *Thermochim. Acta* **659** 203–12
- [22] Sarkar J, Ghosh P and Adil A 2015 A review on hybrid nanofluids: Recent research, development and applications *Renew. Sustain. Energy Rev.* **43** 164–77
- [23] Maddah H, Aghayari R, Mirzaee M, Ahmadi M H, Sadeghzadeh M and Chamkha A J 2018 Factorial experimental design for the thermal performance of a double pipe heat exchanger using Al₂O₃-TiO₂hybrid nanofluid *Int. Commun. Heat Mass Transf.* **97** 92–102
- [24] Moldoveanu G M, Huminic G, Minea A A and Huminic A 2018 Experimental study on thermal conductivity of stabilized Al₂O₃ and SiO₂ nanofluids and their hybrid *Int. J. Heat Mass Transf.* **127** 450–7